

## The Novel Biomaterial of Visible Photoluminescence by Saving Energy Technology of Rapid Thermal Annealing

Jen-Hwan Tsai<sup>1</sup>, Chih-Hsiung Liao<sup>2</sup> and Shen Cherng<sup>3</sup>

<sup>1</sup>Department of Mathematics and Physics, Air Force Academy, Kangshan, Kaohsiung, 820, Taiwan ROC; <sup>2</sup>Department of Physics, Chinese Military Academy, Fengshan, Kaohsiung, 830, Taiwan ROC; <sup>3</sup>Department of Computer Science and Information Engineering, Chengshiu University, Niasong, Kaohsiung, 833 Taiwan, ROC

Received March 20, 2009

### Abstract

In this article, the novel biomaterial of visible photoluminescence by saving energy technology of rapid thermal annealing is presented. A shift in the photoluminescence (PL) peak from blue to near-infrared region was observed in the Si<sup>+</sup>-implanted 400-nm-thick SiO<sub>2</sub> film with the rapid thermal annealing (RTA) method only. As the Si<sup>+</sup>-fluence was 1x10<sup>16</sup> ions/cm<sup>2</sup>, a blue band was observed in the films after RTA at 1050°C for 5 seconds in dry-N<sub>2</sub> atmosphere; then, the band shifted from blue to orange upon increasing the holding temperature of RTA to 1250 °C in the films after the isochronal RTA in dry N<sub>2</sub>. Furthermore, while the fluence was increased to 3x10<sup>16</sup> ions/cm<sup>2</sup> and the holding temperature was at the same range between 1050°C and 1250 °C, the PL peak occurred between red and near-infrared regions. Although the RTA and conventional thermal annealing (CTA) methods produce the similar mechanism, the CTA method needs a much longer annealing-time and a higher Si<sup>+</sup>-implanted dose than the RTA method to observe the same range and intensity of PL peak from the as-implanted sample. Therefore, the RTA method can produce the mechanism in the Si<sup>+</sup>-implanted sample with the energy of PL peak between blue and near-infrared band in palce of the CTA method. [Life Science Journal. 2009; 6(3):61–67] (ISSN: 1097 – 8135)

**Keywords:** rapid thermal annealing (RTA), Si<sup>+</sup> implantation, photoluminescence, SiO<sub>2</sub> films, FTIR spectra

### 1 Introduction

With the advancement of Si technology for electronic integrated circuits and in view of the potential applications in optoelectronics and photonics, there has been a significant interest in the structures consisting of silicon nanocrystals embedded in SiO<sub>2</sub><sup>[1]</sup>. Room temperature visible luminescence had been firstly observed from porous silicon (P-Si), however, several problems have been encountered in practical application<sup>[2, 3]</sup>. The plasma deposition technologies by using silane, gas evaporation, and termination of glass-melt reaction was used to produce visible light emission and silicon nanocrystals, but still none of them were appropriate for the manufacturing process of integrated device products. In addition to above methods, silicon-implantation into SiO<sub>2</sub> film on crystal Si with subsequent conventional thermal annealing (CTA) was another alternative method to fabricate Si-based luminescence structures. Broad emission bands between ~1.5 and ~2.5 eV had been observed by several research groups by implanting Si<sup>+</sup> into the SiO<sub>2</sub> films and following CTA at a temperature higher than 1000°C in vacuum, in Ar, or in N<sub>2</sub><sup>[4-9]</sup>. The 1x 10<sup>17</sup> cm<sup>-2</sup> Si<sup>+</sup>-implanted films after the CTA in dry-N<sub>2</sub> at about 1000°C emits visible blue-light and the PL peaks were shifted from the blue ~2.5 eV to

yellow ~2.2 eV upon increasing the annealing temperature from 1000°C to 1250°C<sup>[5]</sup>. The other light emission between red and near-infrared band was presented at the flux between 1x 10<sup>17</sup> cm<sup>-2</sup> and 3x 10<sup>17</sup> cm<sup>-2</sup> and were attributed to the quantum confinement effect in silicon nanocrystals that was confirmed by transmission electron microscopy<sup>[5-6,8]</sup>. In those reports<sup>[4-9]</sup>, the flux of implanted silicon was relatively high and the whole annealing process required several hours. Although ion implantation of III-V compounds was routinely used in the production of optoelectronic integrated circuits, the methods using silicon implantation seem not suitable for applications in optoelectronics.

Recently, we successfully used the rapid thermal annealing (RTA) method only to observe the photoluminescence (PL) peak between blue and near-infrared regions in the Si<sup>+</sup>-implanted 400-nm-thick SiO<sub>2</sub> films. At the Si<sup>+</sup>-fluence of 1x10<sup>16</sup> ions/cm<sup>2</sup>, the light shifted from blue to orange band when the holding temperature of RTA was increased from 1050°C to 1250 °C in the films after RTA for 5 seconds in dry N<sub>2</sub>. Furthermore, while the fluence was increasing to 3x10<sup>16</sup> ions/cm<sup>2</sup> and the holding temperature was at the same range between 1050°C and 1250 °C, the ranges of PL peak were observed between red and near-infrared regions in the films after the RTA for 20 seconds. On the other hand, by means of RTA and CTA method, the PL

\*Corresponding Author Chih-Hsiung Liao, Ph.D.  
liao550226@yahoo.com.tw

peaks from the Si<sup>+</sup>-implant SiO<sub>2</sub> films were both shifted with the increase of the Si<sup>+</sup> concentration in the oxide matrices and of the thermal annealing duration. However, the shifting affect using RTA method was much better than that using CTA method. In additional, the mechanisms achieved by RTA and CTA are both not dependent on hydrogen-related bonds and have similar existent ratio after isothermal and isochronal RTA test. The results show that the mechanisms in the Si<sup>+</sup>-implanted SiO<sub>2</sub> films after the RTA and CTA methods are similar. However, for the same range and intensity of PL peak from the as-implanted sample, the CTA method needs a much longer annealing-time and a higher dose of Si<sup>+</sup>-implantation than the RTA method. Therefore, using RTA method to produce the mechanisms in the Si<sup>+</sup>-implanted samples with the energy of PL peak between blue to near-infrared band is better than using CTA method.

## 2 Experimental Procedure


Samples were prepared by implantation of Si<sup>+</sup> into a 400-nm-thick wet SiO<sub>2</sub> film which was thermally grown on (100)-oriented p-doped Si substrates. The respective fluences of the Si<sup>+</sup>-implantation are 1x10<sup>15</sup>, 4x10<sup>15</sup>, 1x10<sup>16</sup>, 2x10<sup>16</sup>, and 3x10<sup>16</sup> ions/cm<sup>2</sup>. The temperature of the samples during ion implantation was kept at liquid nitrogen temperature. The acceleration energy of ~160 keV was selected so that the maximum concentration was at a depth of ~250 nm below the surface and the standard deviation of the implanted region was ±60 nm. These samples were subjected to RTA treatments at substrate temperature of 1050°C, 1150°C, and 1250°C, respectively, under dry and wet N<sub>2</sub>. The introduction of wet N<sub>2</sub> into the furnace was performed by heating liquid H<sub>2</sub>O at 100 °C in a cylinder, which was connected to the furnace through a guiding tube, and by mixing up with dry N<sub>2</sub> in the guiding tube. Furthermore, the atmospheric pressure of 50 mbar was provided into the furnace and a heating rate of 100°C/s and the cooling rate of about 100°C /min was used. On the other hand, in order to display the advantage of RTA system, we also annealed the samples at temperatures between 1050°C and 1250°C by using a conventional electric oven. The atmospheric pressure of 50 mbar was provided but a maximum heating rate of 10°C /min and the cooling rate of 50°C /min were used in the CTA system. It shall be noted that the two thermal annealing treatments both include three procedures as heating, holding, and cooling. On the other hand, to detect the PL spectra, a He-Cd laser (3.8 eV) was used as the excitation and a lock-in amplifier was employed to improve the signal-to-noise ratio, in conjunction with a monochromator and cooled photomultiplier tube. The excitation was operated at a small and fixed power of 5 mW to not detect any PL sign in the 3x10<sup>16</sup> cm<sup>-2</sup> Si<sup>+</sup>-implanted 400-nm-thick wet SiO<sub>2</sub> films without RTA. Finally, the FTIR measurements were performed to examine the presence or absence of

hydrogen-related species in samples of oxide film. With the reference being the same silicon plate as the sample, the spectra were measured at room temperature in N<sub>2</sub> atmosphere at a 2 cm<sup>-1</sup> resolution with 200 scan accumulations.


## 3 Results and Discussion

In order to demonstrate that the RTA method is better than the CTA method for producing the mechanism in Si<sup>+</sup>-implanted SiO<sub>2</sub> films with the energy of PL peak between the blue and near-infrared band, the fluence of the silicon implantation in the films was kept at 1x10<sup>16</sup> and 3x10<sup>16</sup> ions/cm<sup>2</sup> and the experimental results are shown in Figs.1 and 2, respectively. From Fig. 1, when the holding temperature of RTA increases from 1050°C to 1250°C in the 1x10<sup>16</sup> cm<sup>-2</sup> Si<sup>+</sup>-implanted 400-nm-thick films after the dry-N<sub>2</sub> RTA for 5 seconds, the PL peak shifted from the blue band of ~2.5 eV to the orange band around 2.1 eV. Furthermore, at the same range of holding temperature as in Fig.1, Fig. 2 shows that the PL peak shifted from the near-infrared band of ~1.85 eV to ~1.5 eV in the 3x10<sup>16</sup> cm<sup>-2</sup> Si<sup>+</sup>-implanted 400-nm-thick films after the dry-N<sub>2</sub> RTA for 20 seconds. Keeping the holding temperature in the range between 1000 °C and 1250 °C, a similar shift of PL peak (~2.5 eV to ~2.3 eV) as shown in Fig. 1 was observed in the 160 Kev Si<sup>+</sup>-implanted 430 nm-thick SiO<sub>2</sub> films after CTA by the group of Mutti. et al.<sup>[5]</sup>. However, the silicon fluence was 1 x 10<sup>17</sup> ions/cm<sup>2</sup> and the duration at those high temperatures was 1 hr. On the other hand, a similar band of PL peak (~1.5 eV) as the result in Fig. 2 were observed in the 150 Kev Si<sup>+</sup>-implanted 800 nm-thick SiO<sub>2</sub> films after CTA at 1100 °C by Garrido et al.<sup>[8]</sup>; but, the silicon fluence must be increased to ~3 x 10<sup>17</sup> ions/cm<sup>2</sup> and the duration at the high temperatures was 8 hr. Besides, At the silicon fluence of 3 x 10<sup>17</sup> cm<sup>-2</sup>, Mutti. et al. can only produce the PL peak of ~1.65 eV in the 160 Kev Si<sup>+</sup>-implanted 430 nm-thick SiO<sub>2</sub> film after CTA at 1000 °C for 5 hrs<sup>[5]</sup>.

Figure 3 shows that the PL peak is shifted from ~2.1 eV to ~1.7 eV when the 3 x 10<sup>16</sup> cm<sup>-2</sup> as-implanted films are treated by the dry-N<sub>2</sub> RTA at 1150°C and the RTA duration is increased from 5 to 20 seconds,. At the same time, Fig. 4 shows that the PL peak is shifted from ~1.75 eV to ~1.7 eV in the 3 x 10<sup>16</sup> cm<sup>-2</sup> as-implanted films after CTA at 1150°C for the duration from 4 to 12 hrs. Referring to Fig.3, the results indicate that the band

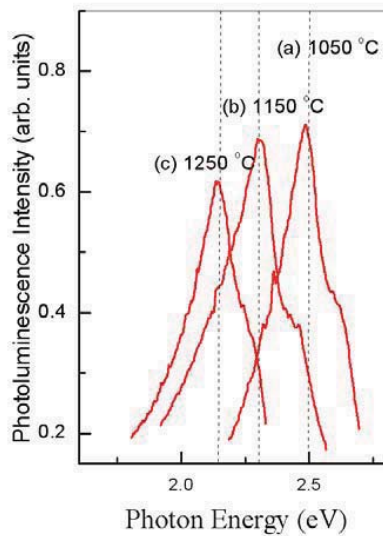

**Figure 1.** PL spectra of the  $\text{Si}^+$ -implanted 400-nm-thick  $\text{SiO}_2$  film grown on crystal Si at a fluence of  $1 \times 10^{16}$  ions/ $\text{cm}^2$  after dry- $\text{N}_2$  RTA for 5 seconds at (a) 1050°C, (b) 1150°C, and (c) 1250°C.

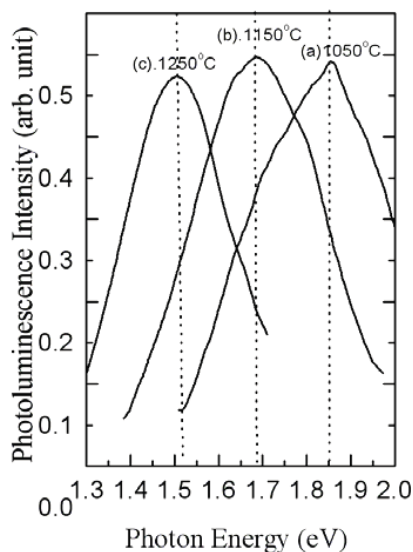


**Figure 2.** PL spectra of the  $\text{Si}^+$ -implanted 400-nm-thick  $\text{SiO}_2$  film grown on crystal Si at a fluence of  $3 \times 10^{16}$  ions/ $\text{cm}^2$  after dry- $\text{N}_2$  RTA for 20 seconds at (a) 1050°C, (b) 1150°C, and (c) 1250°C.


of PL peak can be decreased by increasing the RTA duration. However, the results in Fig. 4 indicate that the PL peak is weakly affected by the CTA duration although the intensity of PL spectra become large due to the increase in CTA duration. The result agrees with that of the study by Shimizu-Iwayama *et al.*<sup>[6]</sup>, in which

the peak energy of the PL is found to be weakly dependent on annealing time, while the intensity of the luminescence increase as the annealing time increases. In addition, comparing Figs. 3 with 4, under the same  $\text{Si}^+$ -flux of  $3 \times 10^{16}$  ions/ $\text{cm}^2$  and holding temperature of 1150 °C, the intensity of PL-peak in the as-implanted film after the RTA method for the holding duration between 5 and 20 seconds as shown in Fig. 3 is always bigger than that after the CTA method for the duration between 4 and 12 hrs as shown in Fig.4.

Figure 5 shows the effect of  $\text{Si}^+$  fluence on the luminescence in the RTA-treated film, where the PL spectrum of the  $\text{Si}^+$ -implanted 400-nm-thick  $\text{SiO}_2$  films grown on silicon crystal at three different fluences after RTA in dry  $\text{N}_2$  at 1150°C for 20 seconds. As the  $\text{Si}^+$  fluence into the as-implanted film was  $1 \times 10^{16}$  ions/ $\text{cm}^2$ , the PL spectrum has a peak at  $\sim 1.95$  eV shown in Fig.5(a); as those films have the fluence of  $2 \times 10^{16}$  and  $3 \times 10^{16}$  ions/ $\text{cm}^2$ , the PL spectra have the peaks at  $\sim 1.8$  eV and  $\sim 1.7$  eV, shown in Figs. 5(b) and 5(c), respectively. The results indicate that the PL peak can be red-shifted with the increase of fluences. The peak energy of the PL spectra is obviously decided by the fluence of the  $\text{Si}^+$ -implantation. Thus, the  $\text{Si}^+$  concentration plays the important role during the production of the respective mechanisms in the RTA-treated films. On the other hand, Fig.6 shows the effect of  $\text{Si}^+$  fluence on the luminescence

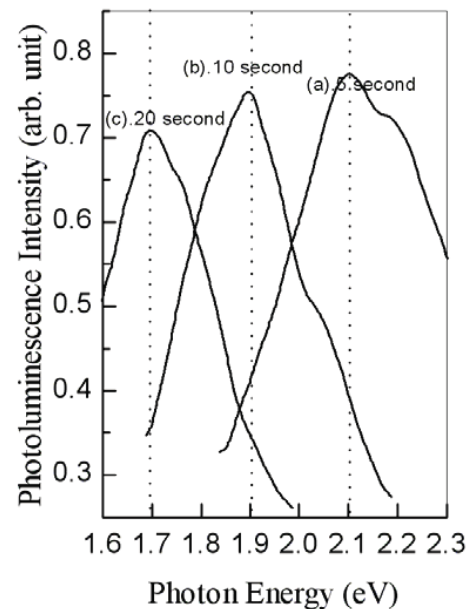


**Figure 3.** The PL spectra of the  $\text{Si}^+$ -implanted 400-nm-thick  $\text{SiO}_2$  film grown on crystal Si at a fluence of  $3 \times 10^{16}$  ions/ $\text{cm}^2$  after dry- $\text{N}_2$  RTA at 1150 °C for (a) 5 seconds, (b) 10 seconds, and (c) 20 seconds.

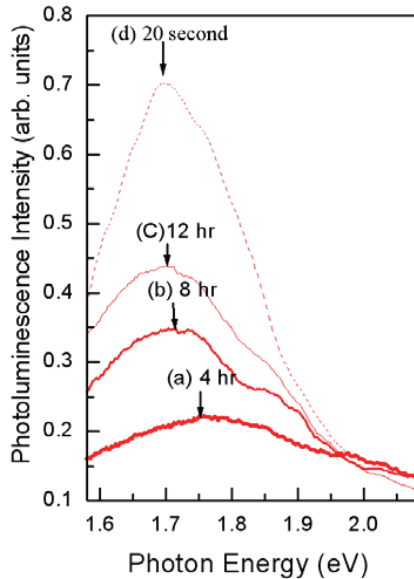


**Figure 4.** The PL spectra of the Si<sup>+</sup>-implanted 400-nm-thick SiO<sub>2</sub> film grown on crystal Si at a fluence of 3x10<sup>16</sup> ions/cm<sup>2</sup> after dry-N<sub>2</sub> CTA at 1150 °C for (a) 4 hours, (b) 8 hours, and (c) 12 hours and (d) after isothermal dry-N<sub>2</sub> RTA for 20 seconds.

in the CTA-treated film, where is also the PL spectrum of the Si<sup>+</sup>-implanted 400-nm-thick SiO<sub>2</sub> films grown on silicon crystal at three fluences as above but after CTA in dry N<sub>2</sub> at 1150°C for 12 hrs. Referring to Figs.5 and 6, under the same holding temperature of 1150°C and the Si<sup>+</sup>-fluence between 1x10<sup>16</sup> and 3x10<sup>16</sup> ions/cm<sup>2</sup>, the PL intensity of the as-implanted film by CTA has obvious increase upon increasing with the dose of implanted Si<sup>+</sup> but the respective PL Peak shifts only from ~1.75 eV to~1.70 eV as shown in Fig.6, which are always weaker than that by RTA as shown in Fig.5. The results show that the intensity of the PL spectrum is obviously affected

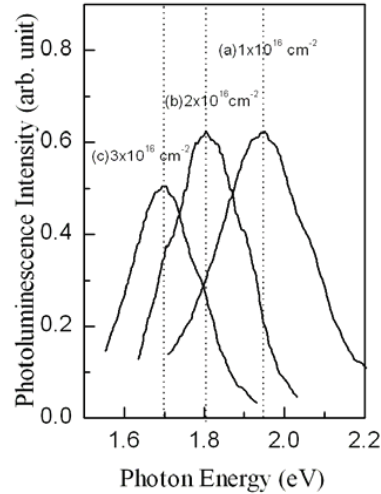

**Figure 5.** PL spectra of the Si<sup>+</sup>-implanted 400-nm-thick SiO<sub>2</sub> film grown on crystal Si at a fluence of (a) 1x10<sup>16</sup> ions/cm<sup>2</sup>, (b) 2x10<sup>16</sup> ions/cm<sup>2</sup>, and (c) 3x10<sup>16</sup> ions/cm<sup>2</sup> after dry-N<sub>2</sub> RTA treatment for 20 seconds at 1150°C.

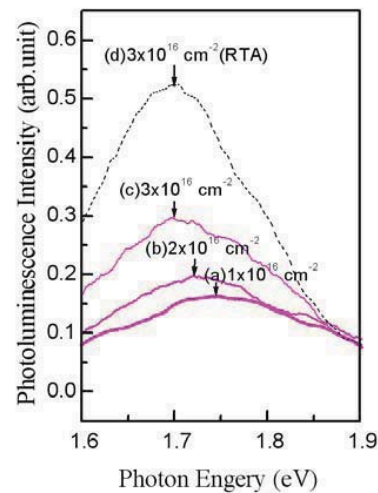

**Figure 6.** PL spectra of the Si<sup>+</sup>-implanted 400-nm-thick SiO<sub>2</sub> film grown on crystal Si at a fluence of (a) 1x10<sup>16</sup> ions/cm<sup>2</sup>, (b) 2x10<sup>16</sup> ions/cm<sup>2</sup>, and (c) 3x10<sup>16</sup> ions/cm<sup>2</sup> after dry-N<sub>2</sub> CTA for 12 hours at 1150°C and at a fluence of (d) 3x10<sup>16</sup> ions/cm<sup>2</sup> after dry-N<sub>2</sub> isothermal RTA for 20 seconds.


by the concentration of implanted Si<sup>+</sup>, but the peak energy is weakly affected by the concentration of implanted Si<sup>+</sup> in the CTA-treated film. Otherwise, the result shown in Fig.6 is consistent with the observation of several other research groups<sup>[6, 8, 14-15]</sup>. According to the observation of Shimizu-Iwayama et al.<sup>[6]</sup>, although

the intensity of PL is strongly affected by the dose of implanted  $\text{Si}^+$ , the peak energy of the PL that is weakly affected by the  $\text{Si}^+$ -dose shifted from 1.75 eV to 1.7 eV as the  $\text{Si}^+$ -fluence implanted into the 600 nm-thick  $\text{SiO}_2$  film with the energy of 180 KeV increases from  $1 \times 10^{16}$  to  $2 \times 10^{17}$  ions/cm<sup>2</sup> and the thermal annealing was carried out by the CTA at 1050 °C for 4 hrs. Furthermore, the shift of PL peak from 1.7 eV to 1.5 eV was observed by Fernandez et al. while the  $\text{Si}^+$ -fluence implanted into the 800 nm-thick  $\text{SiO}_2$  film with the energy of 150 KeV increases from  $1 \times 10^{17}$  to  $3 \times 10^{17}$  ions/cm<sup>2</sup> and the thermal annealing was treated by the CTA at 1100 °C for 8 hrs<sup>[8]</sup>. Anyway, the red-shifting phenomena of PL can be observed by RTA, which can decrease the fluence of the  $\text{Si}^+$ -implantation and shorten the thermal annealing time as compared with CTA. Moreover, although the growth of PL mechanism in the as-implanted  $\text{SiO}_2$  film treated by CTA is much slower than that treated by isothermal RTA, the mechanism in the film treated by the RTA or CTA method is dependent of  $\text{Si}^+$  concentration in the oxide matrices and of the thermal annealing temperature and duration.

Remarkably, besides of the enhanced diffusion and aggregation of  $\text{Si}^+$  implanted in oxide matrix during RTA<sup>[21]</sup>, we believe that the procedure of  $\text{Si}^+$ -nanocrystals formation all be enhanced by using the RTA method but the effect is very sensitive to the heating rate of RTA. According to our initial observation, the PL intensity from the as-implanted film by RTA with the heating rate of 100 °C/s was much stronger than that by RTA with the heating rate of 50 °C/s and no significant intensity could be found after the heating rate of 25 °C/s. At the same time, the shift of PL peak from the as-implanted film by RTA with the heating rate of 100 °C/s could occur at the holding duration less than 20 seconds. However, after the heating rate decreasing to 50 °C/s, the shifting phenomena could occur only at the holding duration less than 5 seconds. The results conform to the observation by Shimizu-Iwayama et al.. They found that, under the  $\text{Si}^+$  fluence of  $\geq 5 \times 10^{16}$  ions/cm<sup>2</sup>, the PL intensity of sample only after RTA at  $\geq 1050$  °C for 5 min with the heating rate of 30 °C/s was much weaker than that treated by the same RTA at first and achieved finally by CTA at  $\geq 1050$  °C for  $\geq 1$  hr<sup>[21]</sup>.

On the other hand, Fig. 7 shows the FTIR spectra of the films with the different treated process. Figure 7(a) shows the FTIR spectrum in the 3750 cm<sup>-1</sup> range of original 400-nm-thick  $\text{SiO}_2$  film grown on the Si crystal without RTA. Besides, for the  $\text{Si}^+$ -implanted 400-nm-thick  $\text{SiO}_2$  films with the same fluence of  $3 \times 10^{16}$  ions/cm<sup>2</sup>, but proceeding the RTA in dry  $\text{N}_2$  at 1150 °C for 20 seconds and the CTA at 1150 °C for 12 hours, the FTIR spectra in the 3750 cm<sup>-1</sup> range are show in Figs. 7(b) and 7(c), respectively. Moreover, in order to confirm the absence of Si-O-H structures in the as-implanted samples by the RTA and CTA, the spectra in the 3750 cm<sup>-1</sup> range of the  $\text{Si}^+$ -implanted 400-nm-thick  $\text{SiO}_2$  films with the respective fluences of  $1 \times 10^{15}$  and  $4 \times 10^{15}$  ions/cm<sup>2</sup> after the RTA but in wet  $\text{N}_2$


are displayed in Figs. 7(d) and 7(e). According to these FTIR spectra in Figs. 7(b) and 7(c), the absorption valleys of Si-O-H structures in the dry- $\text{N}_2$ -annealed films after above RTA and CTA, which are indicated by the signature at  $\sim 3750$  cm<sup>-1</sup> in the FTIR spectra<sup>[16-20]</sup>, are both shallow as the sample of original wet  $\text{SiO}_2$  films without RTA treatment shown as Fig. 7(a) and seem unchange with the increase of silicon implantation fluence. However, from Figs. 7(d) and 7(e), we observed that the absorption valleys of Si-O-H structures in the respective  $1 \times 10^{15}$  cm<sup>-2</sup> and  $4 \times 10^{15}$  cm<sup>-2</sup>  $\text{Si}^+$ -implanted  $\text{SiO}_2$  films after RTA in a wet  $\text{N}_2$  are deepened with the increase of  $\text{Si}^+$ -implantation fluence and so their respective mechanism in the films, that lead to the luminescence, are related closely to the Si-O-H structures<sup>[11, 12]</sup>. In addition, no samples with the above mechanisms in this study display an FTIR signature at  $\sim 2100$  cm<sup>-1</sup> and  $\sim 1450$  cm<sup>-1</sup> (or  $\sim 2300$  cm<sup>-1</sup>), related to the absorption of  $\text{SiH}_x$  ( $x=1,3$ ) and  $\text{CH}_x$  structures, respectively<sup>[13, 16]</sup>. Hence, the above mechanisms in the  $3 \times 10^{16}$  cm<sup>-2</sup>  $\text{Si}^+$ -implanted  $\text{SiO}_2$  films after the above dry- $\text{N}_2$  RTA and CTA are all independent of the Si-O-H related bonds and the  $\text{SiH}_x$  or  $\text{CH}_x$  structures according to the FTIR spectra.

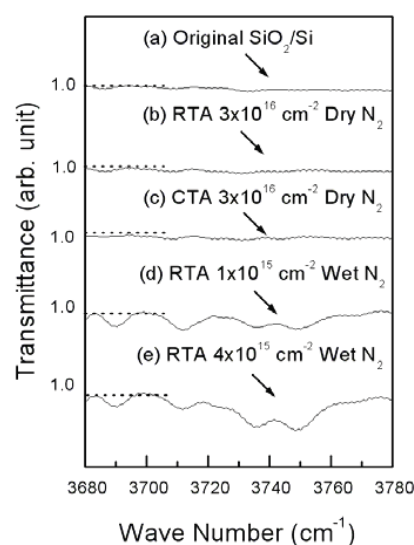

**Figure 7.** FTIR spectra in the 3750 cm<sup>-1</sup> range of (a) original 400-nm-thick  $\text{SiO}_2$  film grown on Si crystal without RTA, the  $\text{Si}^+$ -implanted 400-nm-thick  $\text{SiO}_2$  film grown on crystal Si at a fluence of  $3 \times 10^{16}$  ions/cm<sup>2</sup> (b) after Dry- $\text{N}_2$  RTA at 1150 °C for 20 seconds and (c) after Dry- $\text{N}_2$  CTA at 1150 °C for 12 hours, and that at a fluence of (d)  $1 \times 10^{15}$  ions/cm<sup>2</sup> and (e)  $4 \times 10^{15}$  ions/cm<sup>2</sup> with RTA as in (b) but in wet  $\text{N}_2$ .

Otherwise, Fig. 8 shows the peak-intensity of the PL spectra as a function of the re-annealing temperature by RTA for 5 min in nitrogen. The PL peaks from the respective  $1 \times 10^{16}$  cm<sup>-2</sup> as-implanted films achieved by the CTA (shown as Fig. 8(a)) and RTA (shown as Fig.

8(b)) both decay nearly one-half intensities after isochronal re-annealing at the temperature of 1000 °C and both disappear since the temperature of 1100 °C. Furthermore, when the fluence is increased to  $3 \times 10^{16}$  ions/cm<sup>2</sup>, the PL mechanism in the as-implant films achieved by the CTA (shown as Fig. 8(c)) and RTA (shown as Fig. 8(d)) can persist even after re-annealing at the temperature of >1100°C and both disappear at 1200 °C. The results of the above PL mechanism imply that the ratio of remainder number after the above re-annealing is ambiguously dependent of productive method (RTA or CTA) but depends on the Si<sup>+</sup> dose implanted into the SiO<sub>2</sub> film. Hence, under the same dose of implanted Si<sup>+</sup>, the PL mechanism in the film achieved by RTA and CTA have similar existent ratio after isothermal and isochronal RTA test.

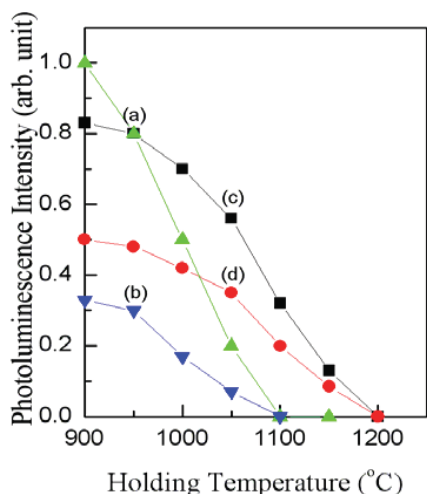

**Figure 8.** Changes in the PL intensity from the  $1 \times 10^{16}$  cm<sup>-2</sup> Si<sup>+</sup>-implanted 400-nm-thick SiO<sub>2</sub> film grown on crystal Si (a) after RTA at 1150°C for 20 seconds and (b) after CTA at 1150°C for 12 hrs and from the  $3 \times 10^{16}$  cm<sup>-2</sup> as-implanted sample (c) after RTA at 1150°C for 20 seconds and (d) after CTA at 1150°C for 12 hrs as a function of the re-annealing temperature, respectively. Re-annealing of these groups of specimens was achieved by RTA for 5 min with heating rate of 30 °C/s.

Finally, both the RTA and CTA methods can produce the mechanisms in the Si<sup>+</sup>-implant SiO<sub>2</sub> film with the energy of PL peak between blue and near-infrared band. In addition, their respective PL peaks are both shifted with the increase of Si<sup>+</sup> concentration in the oxide matrices and of the thermal annealing temperature and duration. The two mechanisms are both independent of hydrogen-related bonds and have the similar existent ratio after the test of RTA at high temperature. Therefore, the respective mechanism in the

Si<sup>+</sup>-implanted SiO<sub>2</sub> films after RTA and CTA are similar. It is well known that Si ion implanted into SiO<sub>2</sub> and subsequent high-temperature CTA induce the formation of embedded luminescence Si nanocrystals<sup>[4-9, 21]</sup>. Hence, the mechanism in the as-implanted film, produced by RTA, was also attributed to silicon nanocrystals embedded in SiO<sub>2</sub>.

#### 4 Conclusion

The PL peak between ~2.5 eV and ~1.5 eV can be observed in the Si<sup>+</sup>-implanted 400 nm-thick SiO<sub>2</sub> film after dry-N<sub>2</sub> RTA only. The studies indicate that light emission in the lower dose Si<sup>+</sup>-implanted film with the ~30 minutes RTA has the similar shifting phenomena like that in the higher dose as-implanted film with the several-hours CTA method. Under the implanted Si<sup>+</sup> dose between  $1 \times 10^{16}$  cm<sup>-2</sup> and  $3 \times 10^{16}$  cm<sup>-2</sup> and the holding temperature of 1150 °C, the intensity of PL spectrum from the as-implanted film treated by the RTA method is always stronger than that treated by the CTA method. Furthermore, light emission from the as-implanted film by the two methods, in which the peak positions are both shifted with the variation of Si<sup>+</sup> concentration in oxide matrices and the thermal annealing temperature and duration. The PL mechanisms in the film achieved by RTA and CTA are both independent of hydrogen-related bonds and have similar existent ratio after isothermal and isochronal RTA test. The phenomena imply that the two methods produce the similar PL mechanism in the oxide matrix, that were both attributed to silicon nanocrystals embedded in SiO<sub>2</sub>. Therefore, using RTA method to produce the mechanisms in the Si<sup>+</sup>-implanted films with the energy of PL peak between blue and near-infrared band is better than using the CTA method.

#### References

1. Brus L, Semiconductors and Semimetals, edited by D. Lockwood (Academic, New York, 1998), Vol. 490, p. 303.
2. Sabet-Darjani R, McAlpine NS and Haneman D, *J. Appl. Phys.* **75** (1994) 8008.
3. Qin G G, Li AP, Zhang BR and Li B, *J. Appl. Phys.* **78** (1995) 2006.
4. Shimizu-Iwayama T, Nakao S and Saitoh K, *Appl. Phys. Lett.* **65** (1994) 1814.
5. Mutti P, Ghislotti G, Bertoni S, Bonoldi L, Cerfolini GF, Meda L, Grilli E and Guzzi M, *Appl. Phys. Lett.* **66** (1995) 851.
6. Shimizu-Iwayama T, Kurumado N, *J. Appl. Phys.* **83** (1998) 6018.
7. Kenyon AJ, Chryssou CE, Pitt CW, Shimizu-Iwayama T, Hole DE, Sharma N and Humphreys CJ, *J. Appl. Phys.* **91** (2002) 367.
8. Fernandez BG, Lopez M, Garcia C, Perez-Rodriguez A, Morante JR, Bonafos C, Carrada M and Claverie A, *J. Appl. Phys.* **91** (2002)

- 798.
9. Chen T P, Lin Y, Tse M S, Fung S and Dong G, J. Appl. Phys. **95** (2004) 8481.
  10. Chou ST, Tsai JH, and Sheu BC, J. Appl. Phys. **83** (1998) 5394.
  11. Tsai JH, Yu AT, and Sheu BC, Jpn. J. Appl. Phys. **39** (2000) L107.
  12. Tsai JH, Yu AT, Jpn. J. Appl. Phys. **44** (2005) 1389.
  13. Allian G, Delerue C, and Lannoo M, J. Lumin. **57** (1993) 239.
  14. Bonafos C, Garrido B, Lopez M, Perez-Rodriguez A, Morante JR, Kihn Y, Ben Assayag G, and Claverie A, Mater. Sci. Eng. **69** (1999) 379.
  15. Agarwal M and Dunham ST, J. Appl. Phys. **78** (1995) 5313.
  16. Shim HW, Kim KC and Seo YH, Nahm K S, Suh E. K, Lee HJ, and Hwang YG, Appl. Phys. Lett. **70** (1997) 1757.
  17. Zveznut ME, Chen TL, Stahlbush RE, Steigerwalt ES, and Brown GA: J. Appl. Phys. **77** (1995) 4329.
  18. Zveznut ME, Chen T L, Appl. Phys. Lett. **69** (1996) 28.
  19. Weng YM, Fan ZN and Zong XF, Appl. Phys. Lett. **63** (1993) 168.
  20. Lin GR and Lin C J, J. Appl. Phys. **95** (2004) 8484.
  21. Iwayama TS, Hama T, Hole DE, Boyd IW, Vacuum, **81**(2006) 179.